



## Mechanical and thermal responses of polyester composites reinforced with different banana fibers orientations developed for industrial applications

<sup>1</sup>George O. Okoronkwo, <sup>2</sup>Chidobere David Nwa-David

<sup>1</sup>Department of Chemical Engineering, Micheal Okpara University of Agriculture, Umudike, Abia State, Nigeria; [okoronkwo.george@mouau.edu.ng](mailto:okoronkwo.george@mouau.edu.ng), [ogeeonyeka@gmail.com](mailto:ogeeonyeka@gmail.com)

<sup>2</sup>Department of Civil Engineering, Micheal Okpara University of Agriculture, Umudike, Abia State, Nigeria; [nwadaid.chidobere@mouau.edu.ng](mailto:nwadaid.chidobere@mouau.edu.ng)

Corresponding Author: [ogeeonyeka@gmail.com](mailto:ogeeonyeka@gmail.com)

**ABSTRACT :** This study investigates the mechanical and thermal responses of polyester composites reinforced with different banana fibers orientations developed for industrial applications. The composites were fabricated and tested for tensile, flexural, and impact properties, as well as thermal conductivity and heat deflection temperature. Results show that composites prepared with banana fiber rope vertical mat (BFRVM) orientation exhibited superior tensile strength (51.9 MPa), flexural strength (261 MPa), and impact strength (22.3 KJ/m<sup>2</sup>) compared to other banana fiber forms and several other natural and synthetic fiber-reinforced composites. The Barcol hardness of BFRVM composites was the highest among the tested composites, indicating robust bonding and enhanced material rigidity. Thermal analysis showed reduced thermal conductivity and improved heat resistance. SEM analysis confirmed strong fiber–matrix adhesion. The results demonstrate that BFRVM composites are viable ecofriendly alternatives to glass fiber composites for industrial applications.

**KEYWORDS:** Banana fiber, Polyester composites, Fiber orientation, Mechanical properties, Thermal conductivity, Sustainable materials

Date of Submission: 22-03-2026 Date of acceptance: 29-04-2026 Date of publication: 30-04-2026

### I. INTRODUCTION

Extensive research has been conducted on synthetic fiber-based polymer composites for various engineering applications, including automotive, marine, aerospace, sports, civil engineering, and household products. However, many of these composites fail to meet environmental sustainability standards. Additionally, the production and market costs of synthetic fibers – especially those incorporating carbon, aramid, and glass fibers – are significantly higher than those of basic polymer matrix materials ((Vignesh et al. 2021), (Ezeokpube et al. 2021)).

To address these challenges, recent research trends have increasingly focused on developing lingo-cellulosic fiber-based polymer composites, attracting significant interest from scientists and engineers worldwide. Ligno-cellulosic fibers offer several advantages over their synthetic counterparts, including lower density, cost-effectiveness, acceptable specific properties, minimal health risks, renewability, and biodegradability ((Manimaran et al.2020), (Kenned et al.2020), (Madu et al. 2019), (Madu et al. 2020)).

In the automotive sector, several major manufacturers – such as Audi, BMW, Daimler Chrysler, Ford, Mercedes-Benz, and Volkswagen – have incorporated lingo-cellulosic fiber-based composites into various vehicle components. For instance, Mercedes-Benz uses coconut fiber-rubber latex composites for seat cushioning in its A-Class model, while the E-Class features flax-sisal fiber mat-reinforced epoxy composites for car door panels. Similarly, Audi employs sisal mat-reinforced polyurethane composites for door trim panels, and Ford integrates kenaf fiber-reinforced composites into the Mondeo model's door panels. The BMW Group has also extensively adopted natural fiber-reinforced composites across its automobile designs, highlighting the growing significance of sustainable materials in the automotive industry ((Akhil et al.2023), (Okoronkwo et al. 2021), (Okoronkwo et al. 2019)).

Researchers worldwide are actively exploring natural fiber composites reinforced with various fiber types, including seed fibers (*e.g.*, cotton, coir), bast fibers (*e.g.*, hemp, flax, kenaf, jute), leaf fibers (*e.g.*, sisal), stem fibers (*e.g.*, banana, coconut, Indian mallow), and grass fibers (*e.g.*, elephant grass, bamboo, wild cane, golden cane) for automotive and industrial applications. Transforming this cellulosic biomass into fibrous reinforcing material for polymer matrices not only adds value, but also alleviates the burden on solid waste management by reducing the volume of waste requiring disposal. Furthermore, the abundant availability of lingo-cellulosic biomass resources can contribute to an increased production rate of reinforcing materials, helping to meet the global demand for lightweight composites suitable for structural applications.9-15 Bio-composites derived from these fibers exhibit high strength and stiffness, excellent thermal and acoustic insulation properties, and notable resistance to fracture.

The performance of lignocellulosic fiber composites depends on multiple factors, including fiber orientation, fiber strength, physical properties, composite processing, and matrix-reinforcement interfacial adhesion. Strength enhancements can be achieved through chemical treatments and hybridization with synthetic fibers ((Bekraoui et al. 2022), (Okoronkwo et al. 2025), (Okoronkwo et al. 2024), (Okoronkwo et al. 2022)). However, despite these advancements, natural fiber composites often exhibit lower strength than their synthetic counterparts. Weaving natural fibers has been shown to significantly improve their mechanical properties, making them comparable to synthetic fiber composites. While some research has been conducted on randomly oriented natural fiber-reinforced polyester composites, studies on naturally woven and man-made woven fiber-reinforced polyester composites remain limited ((Kamarudin et al.2022), (Akteer et al. 2024), (Hossain et al. 2026), (Kusić et al. 2020), (Mahesh et al. 2020)). Literature suggests that woven fiber-reinforced polymer composites generally outperform those with randomly oriented fibers.

This research aimed to evaluate the mechanical and thermal properties of polyester composites reinforced with banana fibers with different orientation, specifically, in random, rope-random, and rope-mat orientations. The study assessed the tensile strength, flexural strength, impact resistance, and Barcol hardness, along with thermal conductivity and heat deflection temperature, of the composites. Scanning electron microscopy (SEM) analysis was conducted to examine fiber-matrix interactions. The findings revealed that banana fiber rope mat-oriented composites exhibited superior mechanical and thermal properties compared to their randomly oriented counterparts, as well as other natural and synthetic fiber composites. SEM analysis confirmed strong fiber-matrix adhesion and efficient stress transfer in rope mat-oriented composites, indicating their potential as effective reinforcement materials.

Based on these results, products were developed for industrial applications, demonstrating the feasibility of using banana fiber rope mats in high-performance composites. Their exceptional strength and heat resistance make them particularly suitable for industrial purposes. This study highlights the potential of banana fiber rope mats in creating sustainable, cost-effective, and high-performance composite materials for diverse industrial applications. This study uniquely evaluates the influence of rope-based fiber architectures (random, rope-random, and rope-mat) on both mechanical and thermal properties of polyester composites.

## II. MATERIALS AND METHODS

### 2.1. Materials

Banana fibers extracted from bark were collected from the local Agricultural and food market at Owerri, Imo State. Figure 1 (a) and (b) illustrates the banana tree and its extracted fibers.

Unsaturated polyester resin was used as the matrix due to its excellent processability, cross-linking properties, and mechanical strength. Cobalt naphthenate and methyl ethyl ketone peroxide (MEKP) were employed as the accelerator and catalyst, respectively. The polyester resin matrix, catalyst, and accelerator were supplied by Ikenna Chemicals Ltd., Nigeria.

### 2.2. Preparation of banana fiber rope mat

The preparation of a banana fiber rope mat involved several steps. Banana fiber was extracted from the pseudo-stems of the banana plant, known for its strength and durability. Harvesting involved stripping the outer layers of the pseudo-stems and soaking the inner parts in water to loosen the fibers, followed by scraping and washing. To convert these fibers into rope, a rope-making machine was used, which consisted of rollers and twisting mechanisms. The cleaned and aligned fibers were fed into the machine, which twisted five individual strands together to form a robust rope. The twisting process ensured the fibers were interlocked, enhancing the rope's durability and resistance to wear. Once the banana fiber rope was ready, it was converted into a mat using a weaving machine automated. The rope was arranged according to the desired mat size and pattern, and the machine interlaced the rope into a mat formation by weaving additional ropes over and under the primary strands. The final steps involved trimming the mat to size and securing its edges to prevent fraying, often through additional stitching or binding.

### 2.3. Fabrication of composites

In this study, composites were fabricated using a combination of chopped banana fiber, banana fiber ropes of 30 mm length, and banana fiber rope mats. The hand lay-up technique was employed for composite preparation to ensure meticulous layering and integration of the fibers. The fabrication process began with maintaining a constant weight fraction of banana fiber relative to the weight of the fiber mat to ensure consistency. The banana fiber rope mat, measuring 300 mm x 300 mm x 3 mm, was placed into a precisely sized mould.



Figure 1(a – d): Preparation of banana fiber rope mat; (a) banana tree, (b) extracted fiber, (c) prepared fiber rope, and (d) woven fiber rope mat

**Table 1: Denotation of prepared polyester composites with different orientation of banana fibers**

Fiber orientation in composite	Denotation
Banana fiber random	BFR
Banana fiber rope random	BFRR
Banana fiber rope horizontal mat	BFRHM
Banana fiber rope vertical mat	BFRVM

Resin, mixed with curing agents to initiate the hardening process, was then poured into the mould cavity, ensuring complete saturation of the fiber mat. Air bubbles, which could compromise the quality of the composite, were carefully removed using a grooved roller. The mould was sealed and subjected to constant pressure to promote uniform curing. The composites were allowed to cure for 24 hours at room temperature, providing sufficient time for the resin to fully bond with the fibers.

For the preparation of randomly oriented chopped banana fiber and banana fiber rope composites, a similar procedure was followed, with extra attention given to achieving a uniform distribution of the fibers within the resin matrix. The different orientations of the banana fiber used in the polyester composites were denoted with symbols, as detailed in Table 1. This comprehensive approach ensured the production of high-quality composites with consistent fiber reinforcement.

## 2.4. Characterization of prepared composites

### 2.4.1. Mechanical characterization

The tensile and flexural strengths of banana fiber mat-reinforced polyester composite samples were evaluated using a universal testing machine (Tinius Olsen H50K). The tensile tests adhered to ASTM D 638-10 guidelines (sample dimensions: 165 mm × 10 mm × 3 mm), performed at a crosshead speed of 1 mm/min, while the flexural tests followed ASTM D790-10 standards (sample dimensions: 127 mm × 13 mm × 3 mm), at a crosshead speed of 2 mm/min.

Impact testing was performed using a Tinius Olsen (Model: 104) machine, following ASTM D 256-10 (sample dimensions: 65 mm × 13 mm × 3 mm).

The hardness of the composite plates was examined using a Barcol Hardness Tester (Model: VBH2), following the ASTM D2583 standard.

Each test was conducted five times, and the average values were calculated for further analysis.

### 2.4.2. Fractography analysis

A SEM instrument, operating at an acceleration voltage of 20 to 40 kV, was used to analyze the fractography of composite samples after tensile, flexural, and impact tests. The fractured regions were first cut into 10 × 10 mm squares and then coated with a thin gold layer to improve conductivity.

### 2.4.3. Thermal characterization

Thermal conductivity tests were conducted to assess the heat transfer properties of the composite materials, specifically measuring the transverse thermal conductivity using a guarded heat flow meter (Unitherm Model No. 2022) in accordance with ASTM E 1530 standards. The test samples were precisely cut from the fabricated composites into discs, with a diameter of 50 mm and a thickness of 3 mm, to fit the testing equipment. Each sample was placed into the thermal conductivity apparatus, where it was subjected to a mean temperature of 55 °C and a compressive load of 0.28 MPa. This setup ensured that the sample was under controlled conditions for accurate measurement. The testing procedure involved reaching thermal equilibrium, which was crucial for obtaining precise and consistent results. Once thermal equilibrium was achieved, the temperature difference across the sample was measured, and the output from the heat flux transducer was recorded. The heat flux transducer provided data on the rate of heat flow through the sample, which, combined with the measured temperature gradient, allowed for the calculation of the sample's thermal conductivity. This property indicates how effectively the composite material can conduct heat, providing valuable insights into its performance in thermal management applications.

The heat deflection temperature (HDT) test was implemented using an HDT-Vicat tester (XRW300A, Chengde Jinhe Instrument Manufacturing Co., Ltd., Chengde, China) according to ASTM D 648 (60 mm × 12 mm × 3 mm) standard.

### III. RESULTS AND DISCUSSION

Table 2 presents a comparison of the physico-chemical properties of banana fibers with those of other banana fiber varieties. Banana fibers contain the highest cellulose content (59.22 wt. %) among the listed varieties, indicating superior tensile properties and suitability for reinforcement applications. Their composition includes 59.22 wt. % cellulose, 12.09 wt. % hemicelluloses, 14.39 wt. % lignin, and 2.69 wt. % pectin. The mechanical properties of lignocellulosic fibers are significantly influenced by their chemical composition. The high  $\alpha$ -cellulose content (59.22 wt. %) enhances the mechanical strength of banana fibers, while the relatively low hemicellulose content (12.09 wt. %) supports strong attachment to cellulose micro-fibrils, likely through hydrogen bonding. Additionally, the elevated lignin content (14.39 wt. %) protects against biological degradation and contributes to the structural integrity of the fibers. These properties make banana fibers a viable alternative to conventional natural fibers, such as sisal, coir, flax and cotton. They show great potential as reinforcement materials for lightweight applications across various engineering industries, including construction, automotive, and aerospace.


**Table 2: Chemical composition of different banana cultivars**

Name of variety	Cellulose (wt. %)	Hemicelluloses (wt. %)	Lignin (wt. %)	Pectin (wt. %)
Grand Naine	48.19	15.91	19.17	3.46
Poovan	57.57	12.65	16.71	2.82
Monthan	48.55	15.75	21.56	4.08
Banana	59.22	12.09	14.39	2.68

#### 3.1. Mechanical characterization

##### 3.1.1. Tensile properties


The tensile properties of various banana fiber-reinforced polyester composites were systematically evaluated, and the results are detailed in Figure 2.

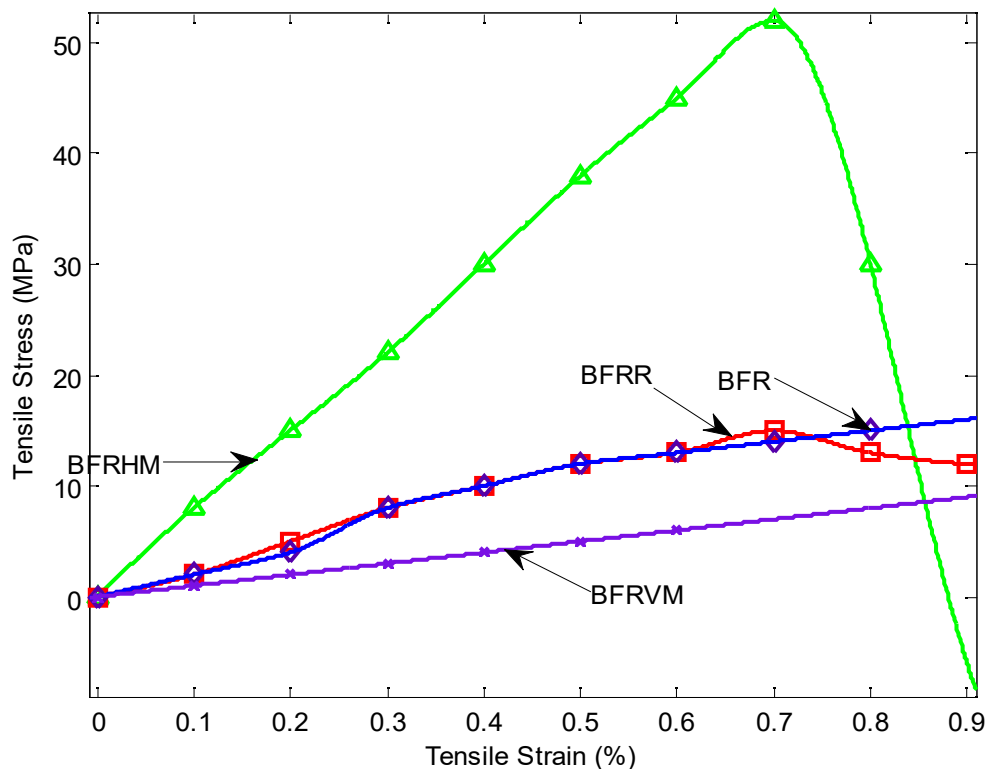

**Figure 2(a): Stress - strain curves of the four different composites**


Figure 2(a) illustrates the typical stress-strain curves for the composites reinforced with banana fiber in various orientations: banana fiber random (BFR), banana fiber rope random (BFRR), banana fiber rope horizontal mat

(BFRHM), and banana fiber rope vertical mat (BFRVM). The curves demonstrate that stress increases linearly with strain for all composites. However, the BFRVM composites exhibit a distinctive behavior: after reaching a high stress point, the stress suddenly decreases, indicating a ductile response. This behavior is characteristic of ductile materials and suggests that the BFRVM composites experience a yield point, beyond which they can endure more strain before ultimate failure.

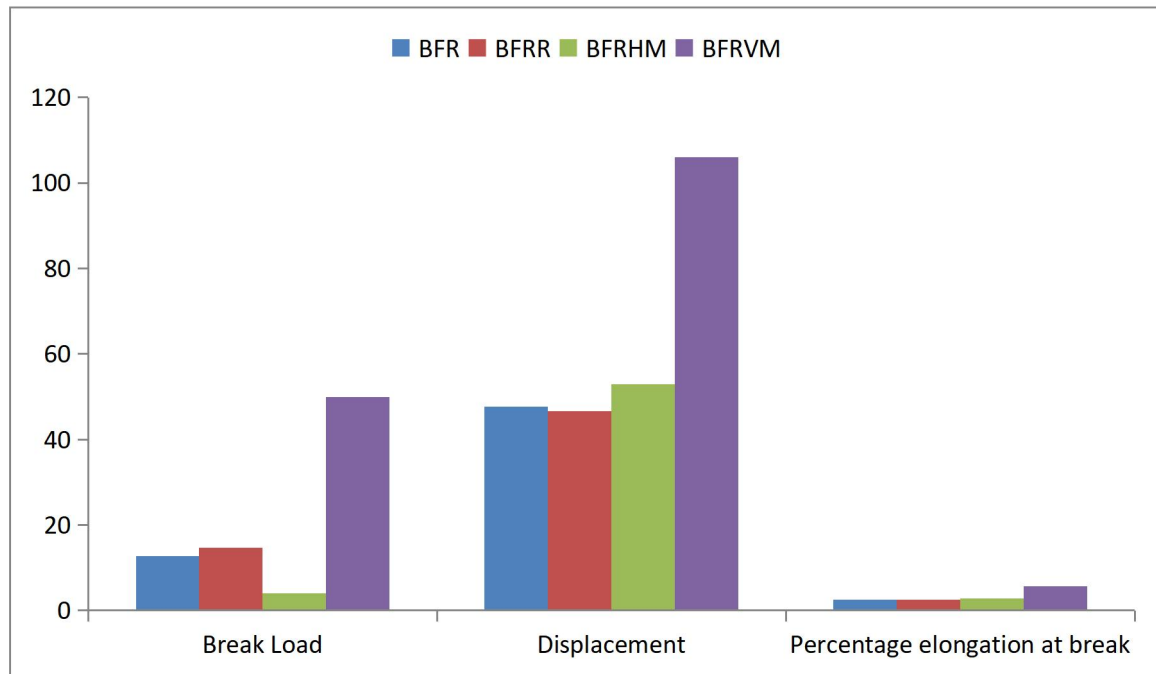

**Figure 2(b): Break load, maximum displacement and percentage elongation at break of the four different composites**

Figure 2(b) presents key tensile properties, including break load, maximum displacement, and percentage elongation at break. The BFRVM-reinforced polyester composites show a significantly higher break load, approximately 3.94 times that of BFR, 3.41 times that of BFRR, and 13.27 times that of BFRHM composites. This demonstrates a superior ability to withstand tensile forces before breaking. Similarly, the maximum displacement, which reflects the composite's ability to deform under stress, was about 2.23 times higher than that of BFR, 2.27 times higher than that of BFRR, and twice higher than that of BFRHM composites. The higher maximum displacement of BFRVM composites highlights their greater ductility and ability to sustain more strain before failure. The percentage elongation at break for BFR, BFRR, BFRHM, and BFRVM composites were 2.56 %, 2.52 %, 2.85 %, and 5.71 %, respectively. The BFRVM composites exhibited the highest percentage elongation, indicating that they can endure more strain compared to the other composite types before reaching failure.

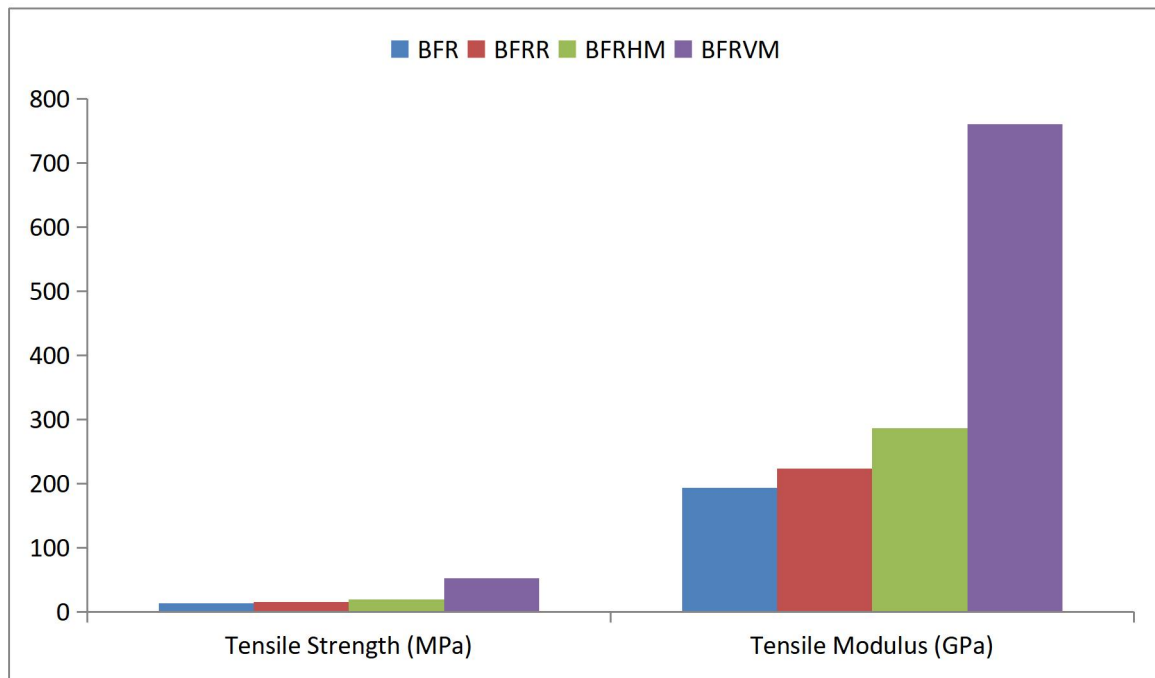

**Figure 2(c):** Tensile strength and tensile modulus of the four different composites

Figure 2(c) shows the tensile strength and tensile modulus of the composites. The tensile strength values were 13.2 MPa for BFR, 15.2 MPa for BFRR, 19.5 MPa for BFRHM, and 51.9 MPa for BFRVM-reinforced polyester composites. The BFRVM composites demonstrated the highest tensile strength approximately 3.93 times that of BFR, 3.4 times that of BFRR, and 2.66 times that of BFRHM composites. This increase in tensile strength is attributed to the enhanced interfacial bonds between the matrix and the fibers, which effectively resist fiber pullout and rupture. The tensile modulus, indicating the stiffness of the composite, followed a similar trend, with BFRVM composites exhibiting the highest value among the types tested. This suggested that the mat form orientation improves the composite's resistance to deformation and breaking under tensile stress.

Figure 3(a – b) provides SEM fractography images of tensile fractured samples of banana fiber rope mat composites, showing detailed features such as fiber bending, fiber pullout, and complex crack propagation. The SEM images revealed that the fibers were well-bonded with the surrounding resin, which contributed to the enhanced tensile strength and durability of the composite. The presence of a well-enriched resin matrix around the fibers was crucial for improving the overall strength and performance of the composite.

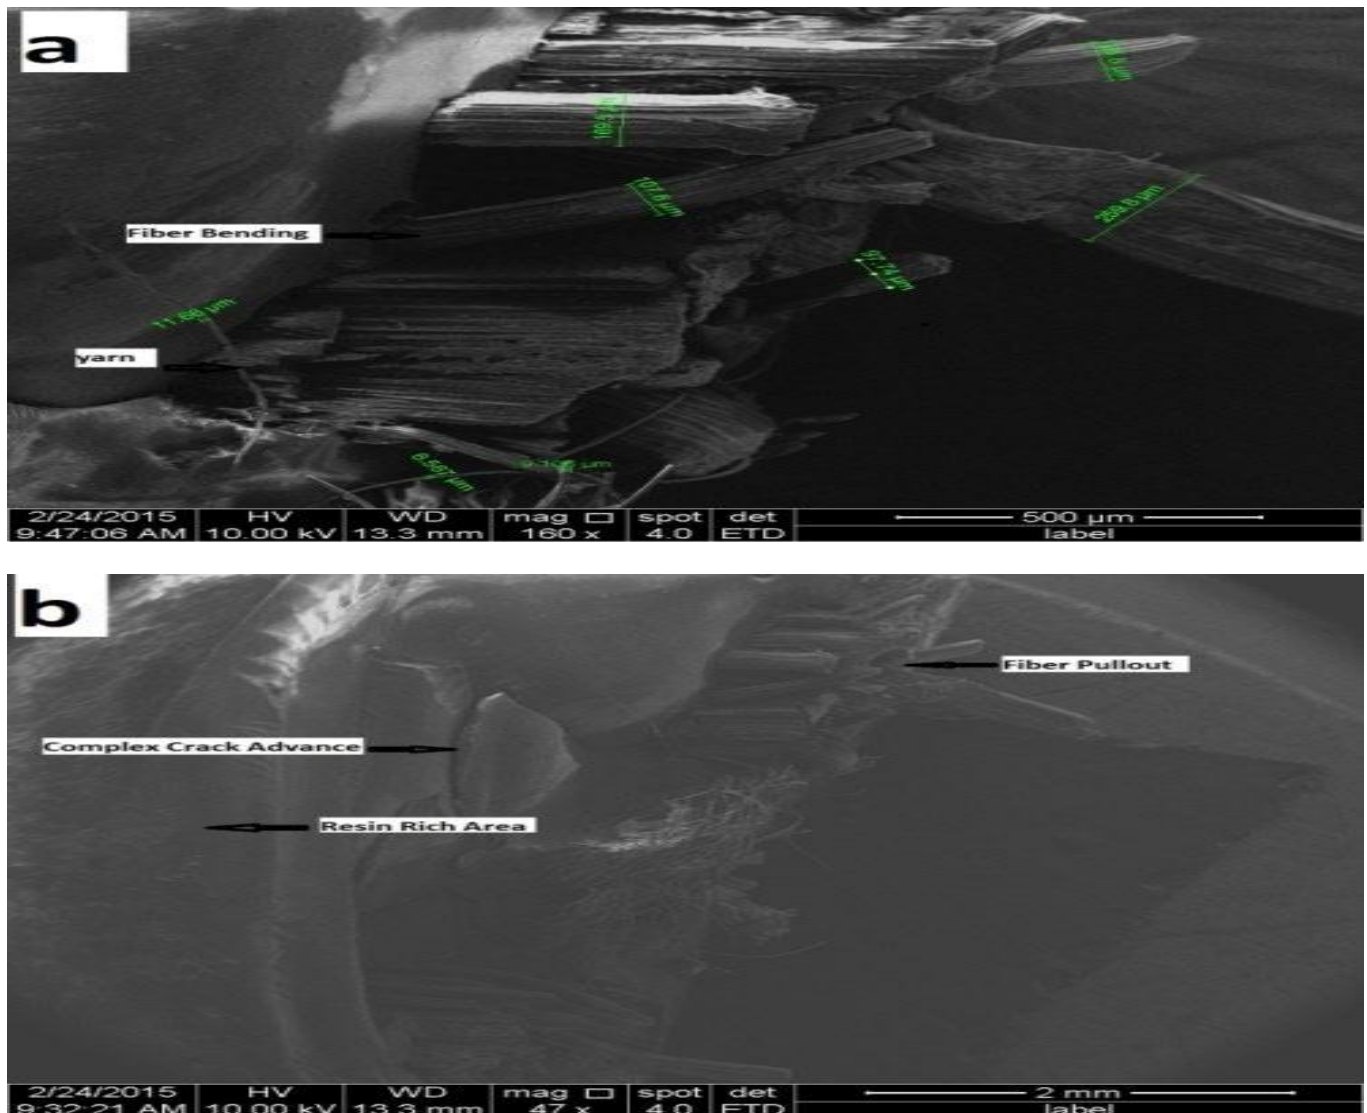


Figure 3(a - b): SEM images of tensile-tested samples of banana fiber mat composites (a = 100x, b = 47x)

Overall, the tensile properties of the BFRVM-reinforced polyester composites were superior to those of other natural fiber-reinforced polyester composites (randomly oriented, 12, 13, 21 unidirectionally oriented 1 and woven 4, 23) and were comparable to, or exceed, the performance of glass fiber composites (GFC) in terms of tensile strength and modulus. This highlighted the effectiveness of the mat form orientation of banana fibers in enhancing the mechanical properties of the composites, making them a competitive alternative to traditional glass fiber composites for various applications.

### 3.1.2. Flexural properties

The flexural properties of banana fiber-reinforced polyester composites were thoroughly evaluated and are presented in Figure 4.

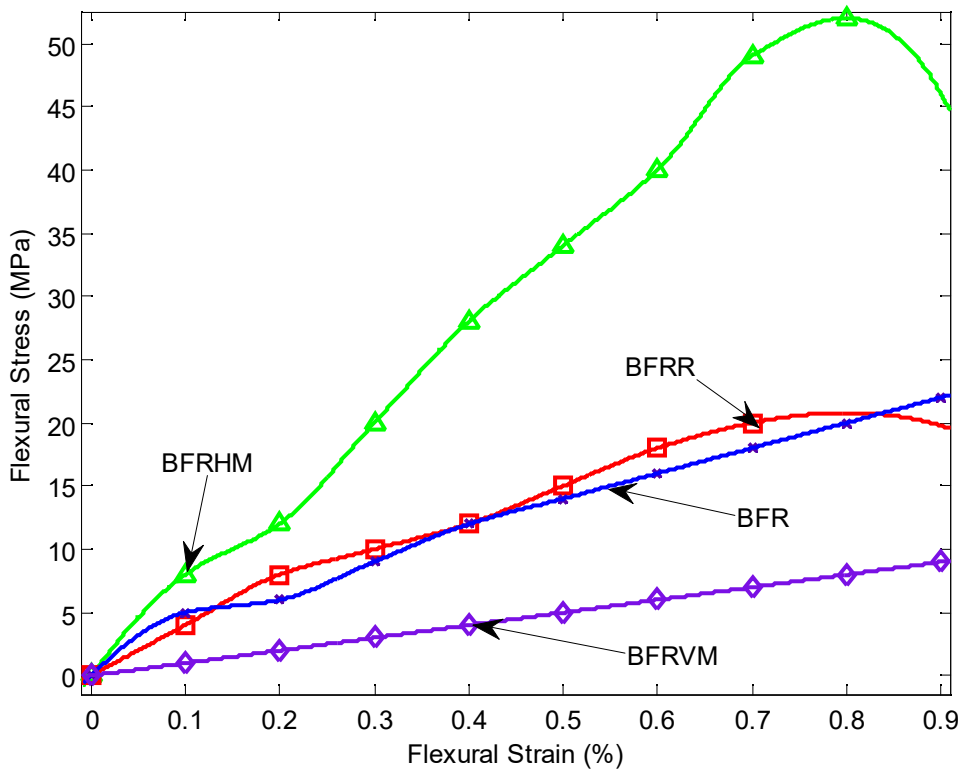


Figure 4(a): stress - strain curves of the four different composites

The stress-strain behavior of the composites under flexural loading, shown in Figure 4(a), illustrated that the BFRVM-reinforced polyester composites exhibited a notable plasticizing effect due to the high extensibility of the banana fiber ropes. This effect imparts significant stiffness and flexibility to the otherwise brittle polyester matrix, enabling the BFRVM composites to better withstand applied stresses and delay or prevent composite failure compared to the other formulations of composites.


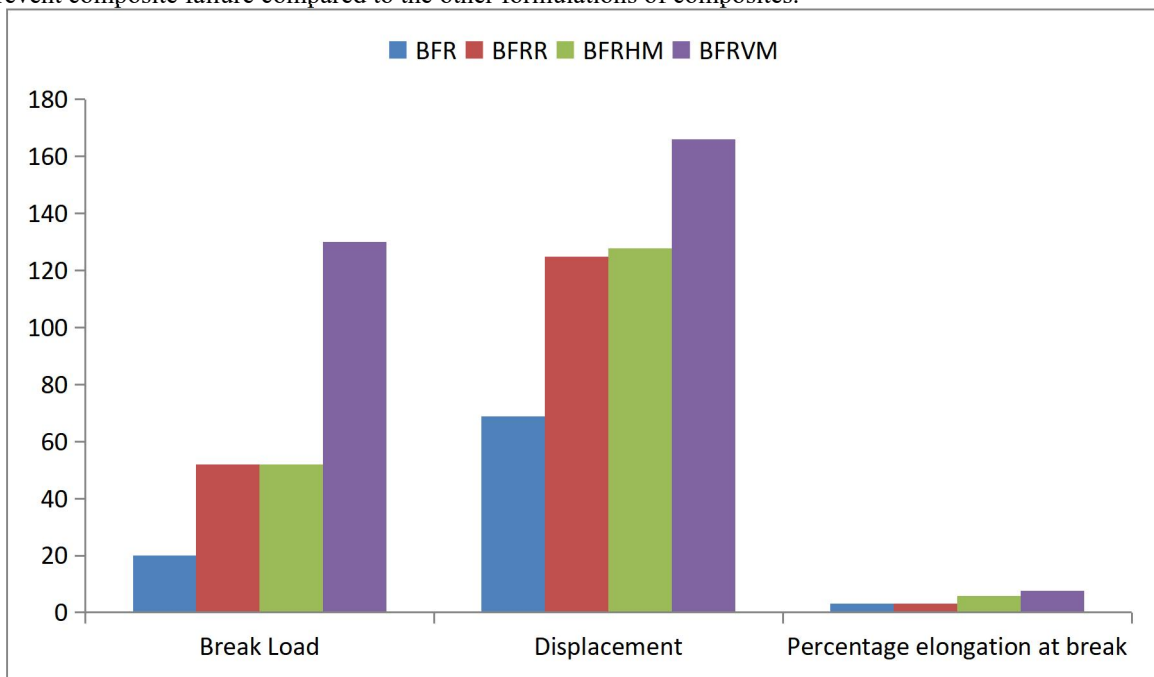


Figure 4(b): break load, maximum displacement and percentage elongation at break of the four different composites


Figure 4(b) details key flexural properties, including break load, maximum displacement, and percentage elongation at break. The BFRVM composites demonstrated the highest break load, approximately 6.5 times greater than that of the BFR composites and 2.5 times greater than those of both the BFRR and BFRHM composites. This indicated a superior ability to bear loads before failure. Similarly, the maximum displacement of 166 BFRVM composites was about 2.41 times higher than that of the BFR and BFRR composites, and 1.33 times greater than the BFRHM composites, reflecting their enhanced capacity to deform under stress. The percentage elongation at break for the BFRVM composites was also significantly higher 2.38 times greater than those of BFR and BFRR composites, and 1.3 times greater than that of BFRHM composites indicating increased ductility and strain tolerance.

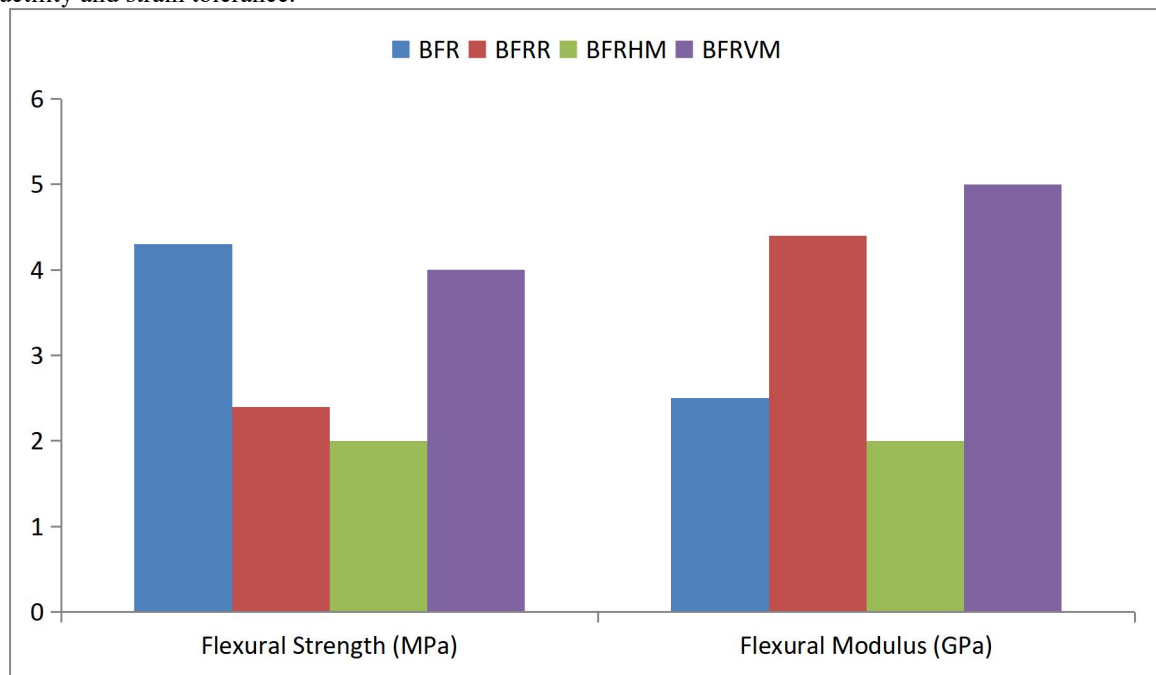

**Figure 4(c):** flexural strength and flexural modulus of the four different composites

Figure 4(c) presents the flexural strength and flexural modulus of the composites. The BFRVM composites exhibited the highest flexural strength at 261 MPa, which is approximately 6.69 times that of the BFR and BFRHM composites, and 2.5 times that of the BFRR composites. This superior flexural strength is attributed to the mat orientation of the banana fiber ropes, which enhanced the adhesion between the fibers and the polyester matrix, thereby improving the composite's ability to resist bending stresses. The flexural modulus, which measures the stiffness of the composite, was also the highest for the BFRVM composites at 20.4 GPa, marginally surpassing the other composites: 6.01 GPa for BFR, 17.8 GPa for BFRR, and 10.1 GPa for BFRHM composites.

Figure 5(a – b) provides SEM images of the fractured flexural samples for banana fiber rope mat composites, revealing details such as fiber fracture, interfacial gaps, and fibers detached from the matrix. The reduced occurrence of voids in the matrix suggested better consolidation and bonding, which contributed to the higher flexural strength observed. The SEM images further highlighted that the improved fiber-matrix adhesion and reduced void content were key factors in the enhanced mechanical performance of the BFRVM composites.

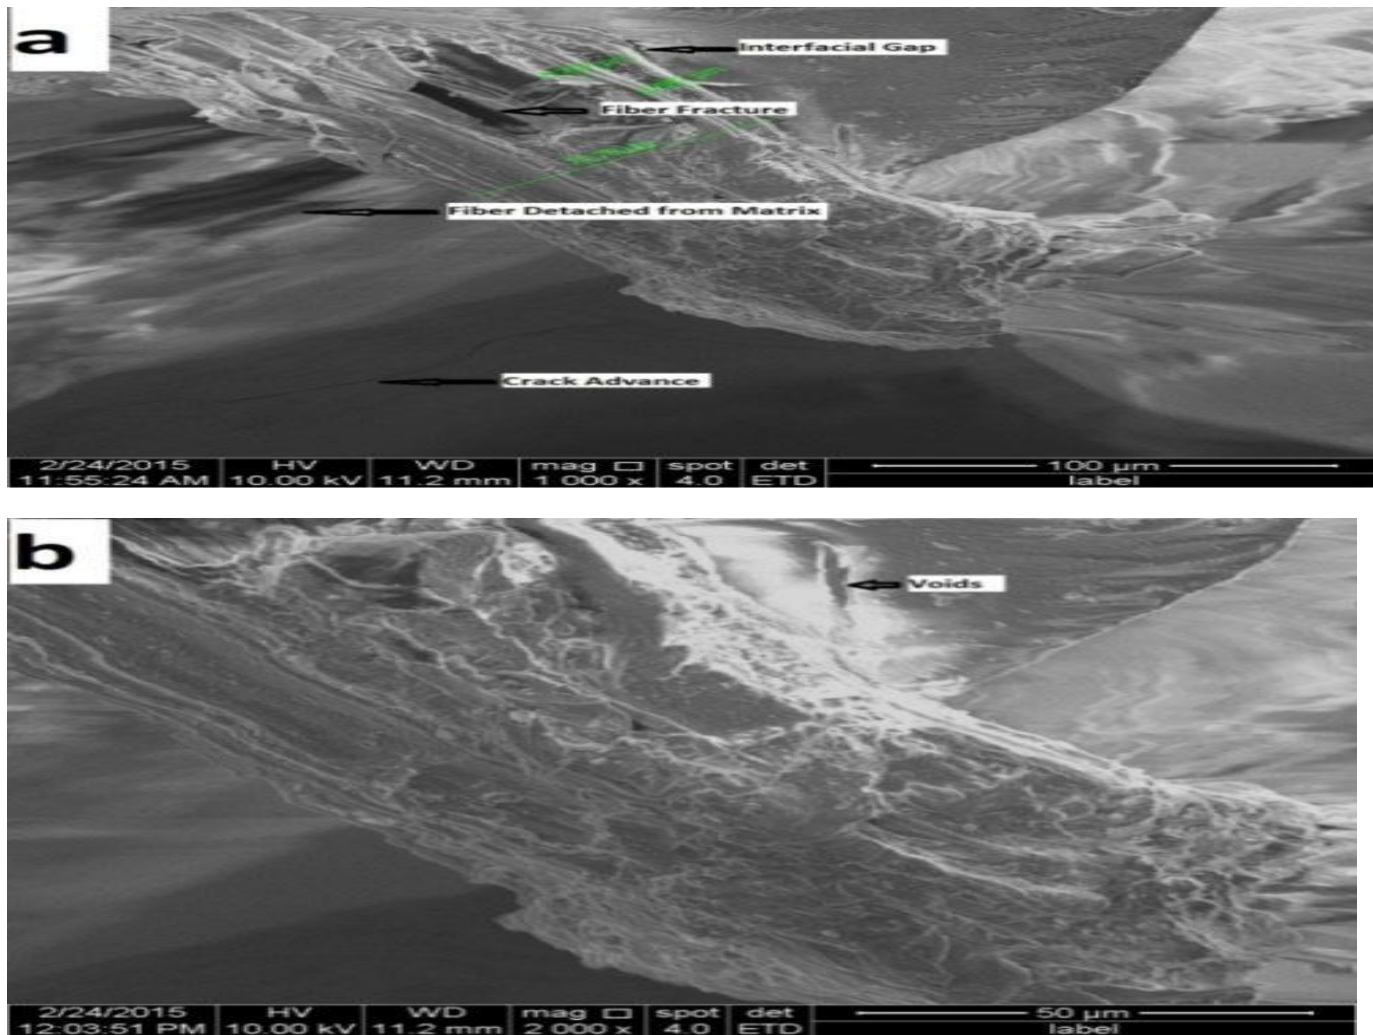


**Figure 5(a - b):** SEM images of flexure-tested samples of banana fiber mat composites (a = 1000x, b = 2000x)

Overall, the flexural properties of the BFRVM-reinforced polyester composites not only surpass those of other natural fiber-reinforced polyester composites, but also approach or exceed the performance of glass fiber composites (GFC), including those with random, unidirectional, and woven orientations (randomly oriented, 13, 14, 19, 21 unidirectionally oriented 1, 2, 4 and woven). This demonstrates the effectiveness of the banana fiber rope mat orientation in achieving high flexural strength and stiffness, making it a competitive alternative for applications requiring robust mechanical performance.

### 3.1.3. Impact strength

The impact strength test was conducted to evaluate the ability of different banana fiber-reinforced polyester composites to withstand sudden loads, as depicted in Figure 6. The impact strengths of the composites were measured as 3.35, 3.96, 5.8, and 22.3 kJ/m<sup>2</sup> for the BFR, BFRR, BFRHM and BFRVM composites, respectively. These results highlighted a significant variation in impact resistance among the different composite types. The BFRVM-reinforced polyester composites showed the highest impact strength, showcasing an exceptional ability to absorb and disperse impact energy. Specifically, the impact strength of BFRVM composites was approximately 6.65 times greater than that of BFR composites, 5.63 times greater than BFRR composites, and 3.84 times greater than BFRHM composites.

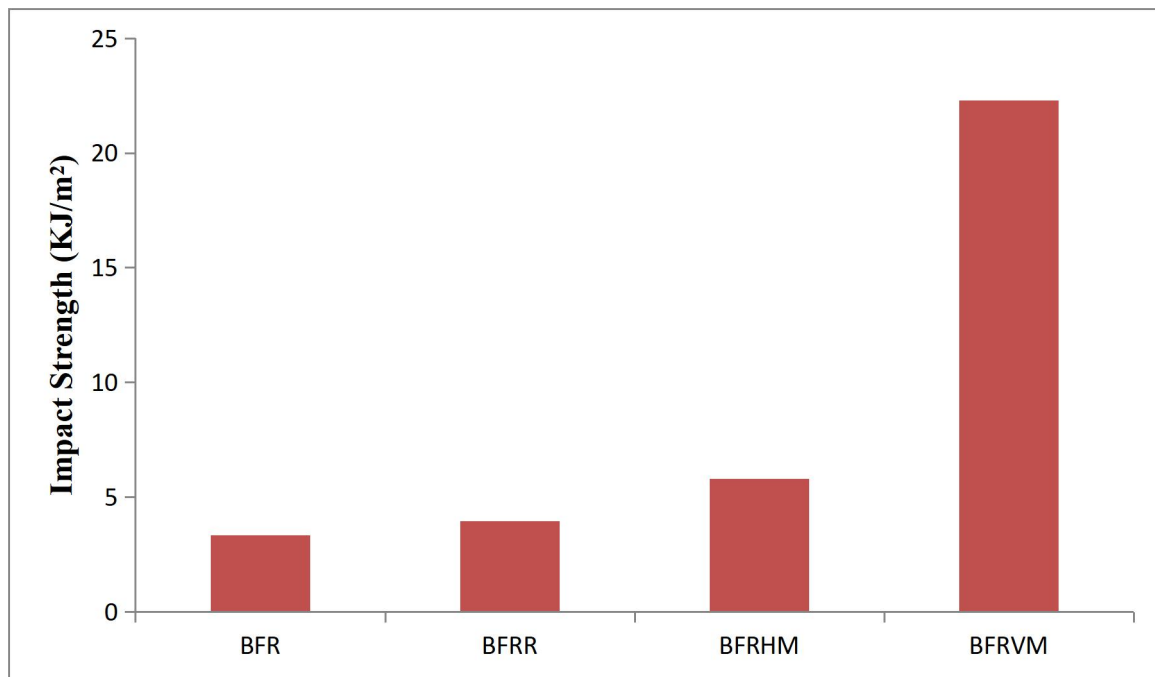

**Figure 6:** Impact strength for different fiber reinforced composites

The enhanced impact strength of the BFRVM composites can be attributed to the presence of long banana fiber ropes, which contribute to a more effective distribution and absorption of impact energy. The longer fibers in the mat form enhance the composite's ability to dissipate impact forces over a larger area, thereby reducing the likelihood of catastrophic failure upon impact.

Figure 7(a –b) provides SEM images of the fractured impact samples of banana fiber rope mat composites, revealing detailed features of the failure surfaces. The SEM analysis shows clear signs of porous structures, fiber fractures, and fiber bending. The examination also confirms that the individual fibers within the mat were twisted together during the rope-making process, contributing to the composite's overall impact resistance. The SEM images provide visual evidence of how the fiber arrangement and bonding contribute to the material's performance under impact conditions.

The impact strength results for the BFRVM composites were notably higher compared to other randomly oriented and woven natural fiber-reinforced polyester composites, and were found to be quite close to that of glass fiber composites (randomly oriented 14, 19, 21 and woven 4, 15). This indicated that BFRVM composites offer competitive impact resistance, positioning them as a strong alternative to traditional glass fiber composites in applications requiring high impact durability. This superior performance underscores the effectiveness of using long fiber ropes in enhancing the mechanical properties of composite materials.

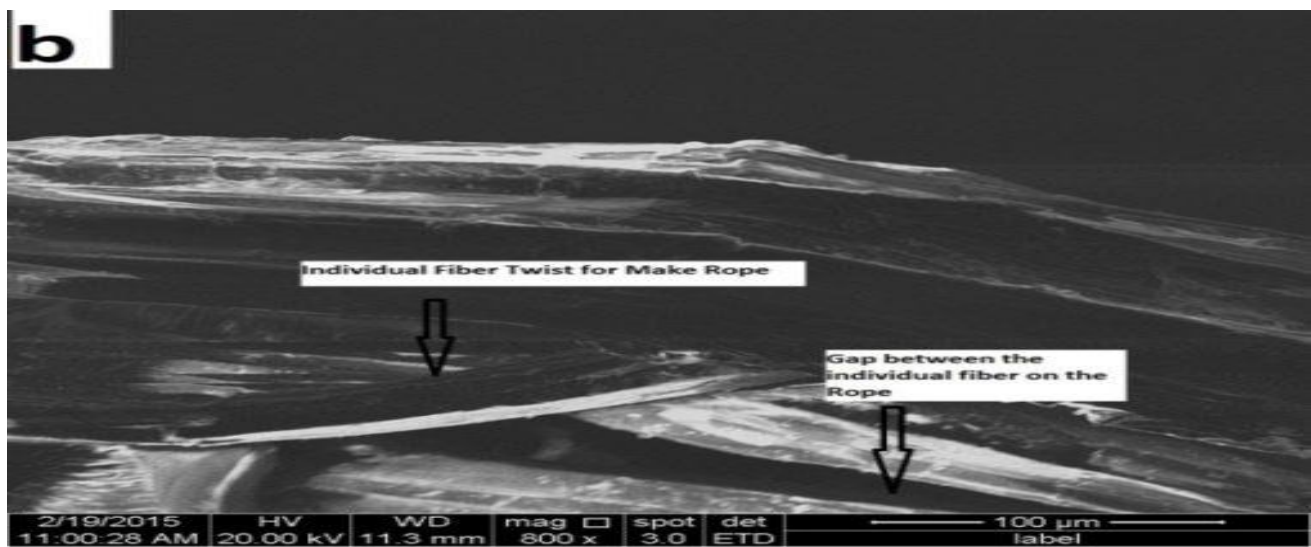
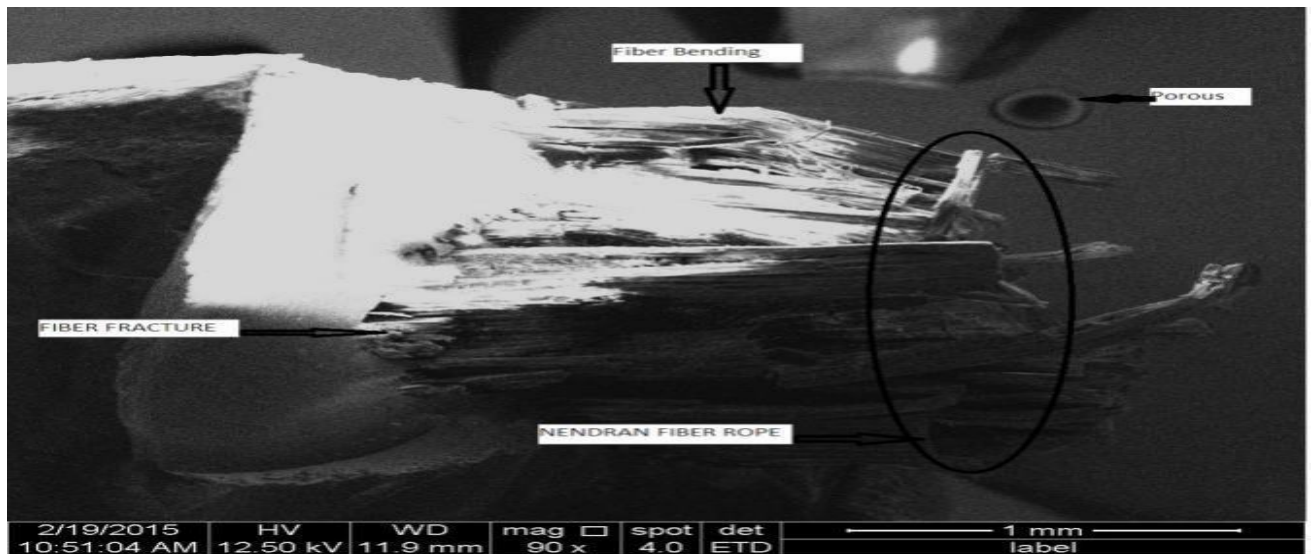


Figure 7(a - b): SEM images of impact-tested samples of banana fiber mat composites (a = 90x, b = 800x)

Table 3: Comparison of mechanical properties of the banana fiber polyester composites prepared in this study with those of glass fiber and other natural fiber-reinforced polymer composites

Fiber/matrix	Fiber orientation	Tensile strength (Mpa)	Flexural strength (Mpa)	Impact strength (KJ/m <sup>2</sup> )	Barcol hardness
	NFR	13.2	39	3.35	22
Nendran fiber/polyester	NFRR	15.2	104	3.96	25
	NFRHM	19.5	40	5.8	30
	NFRVM	51.9	261	22.3	39
Water hyacinth/polyester	Random	23.4	41.8	---	---
Indian areca fruit husk/polyester	Random	68.20	73.9	6.82	---
<i>Sansevieria cylindrica</i> /polyester	Random	75	83.85	9.45	---
Palmyra palm/polyester	Random	18.7	51.1	16	---
Sisal/polyester	Random	55	84	11	---
Bagasse/polyester	Random	17-23	31-48	---	---
Wildcane grass/polyester	Unidirectional	---	111	---	---
Waste groom/polyester	Unidirectional	94.08	---	---	---
Jowar/polyester	Unidirectional	124	134	---	---
Bamboo/polyester	Unidirectional	126	128.5	---	---

Coconut sheath/polyester	Naturally wov	60	107.9	12.97	---
Banana/polyester	Woven	75	80	19	---
Kenaf/polyester	Woven	110-120	100-110	20-23	---
Rattan/polyester	Woven	20.43	57.65	---	45
GF/epoxy	Woven	83	132	52.66	---

### 3.1.4. Barcol hardness

Figure 8 illustrates the variation in Barcol hardness values for different forms of banana fiber-reinforced polyester composites, revealing how the orientation and form of reinforcement affect the material's hardness. The measured hardness values were 22, 25, 30, and 39 for the BFR, BFRR, BFRHM, and BFRVM composites, respectively. Among these, the BFRVM-reinforced polyester composites demonstrated the highest hardness value, significantly surpassing the other composite types. Specifically, the hardness of the BFRVM composites was approximately 1.77 times greater than that of the BFR composites, 1.56 times greater than that of the BFRR composites, and 1.3 times greater than that of the BFRHM composites.

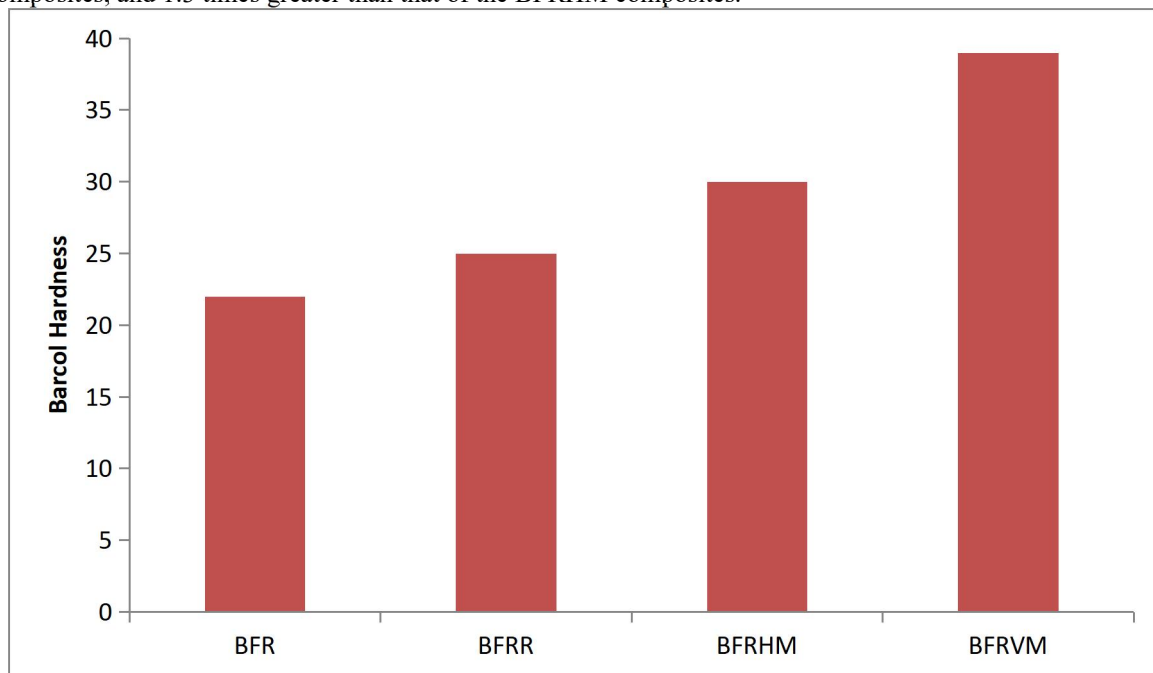



Figure 8: Barcol hardness for different forms of composites

This substantial increase in hardness observed in the BFRVM composites is indicative of a stronger bonding between the matrix and the banana fiber ropes used in the mat weaving. The higher hardness values suggested that the BFRVM composites have enhanced resistance to surface indentation and deformation, which can be attributed to the more effective integration and reinforcement provided by the fiber mat. This improved hardness not only reflects the quality of the bond between the matrix and reinforcement, but also indicates better overall mechanical performance of the composite. The increased hardness of the BFRVM composites makes them suitable for applications requiring greater surface durability and resistance to wear, thus highlighting the benefits of using the woven mat orientation for enhancing the properties of the composite material.

### 3.1.5. Thermal characterization

#### 3.1.5.1. Thermal conductivity

The thermal conductivity of the four types of banana fiber-reinforced polyester composites BFR, BFRR, BFRHM, and BFRVM was systematically measured and presented in Figure 9. The results indicated thermal conductivities of 0.151, 0.166, 0.14, and 0.14  $\text{Wm}^{-1}\text{K}^{-1}$ , respectively, for each composite type. Notably, the thermal conductivity of the BFRHM and BFRVM composites were lower compared to the BFR and BFRR composites. Specifically, the thermal conductivity decreased by 9.2% and 15.6% for BFRHM and BFRVM composites, respectively, relative to their randomly oriented counterparts BFR and BFRR.

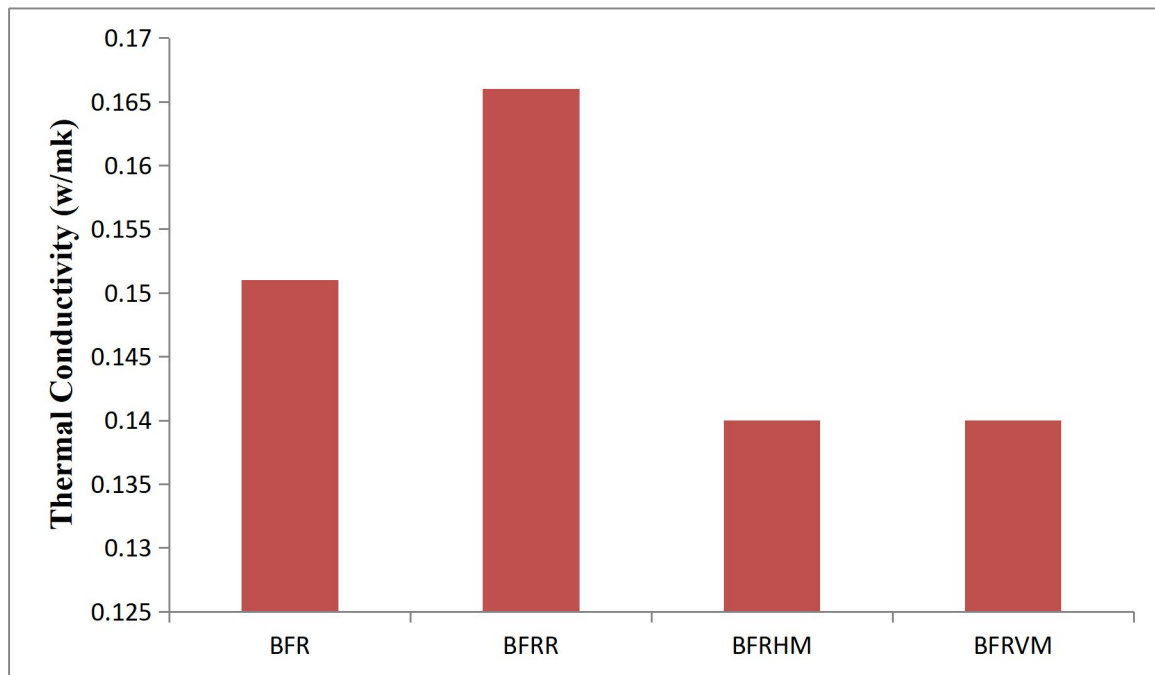


**Figure 9:** Thermal conductivity for different forms of composites

This reduction in thermal conductivity observed in the BFRHM and BFRVM composites attributed to the woven mat orientation of the banana fiber ropes. In these composites, the weaving of the mat created a more uniform and less thermally conductive structure, compared to the random fibers found in the BFR and BFRR composites. The mat arrangement of the fibers contributed to a more effective thermal insulation barrier, thus reducing the overall heat transfer through the material.

The lower thermal conductivities of the BFRHM and BFRVM composites were particularly advantageous for applications involving exposure to high temperatures or hot surfaces. This improved thermal insulation enhanced the material's performance in thermal management applications by minimizing heat transfer and protecting underlying structures from heat damage. Thus, the orientation of the banana fiber ropes played a critical role in optimizing the thermal properties of these composites, making them suitable for specific thermal applications where heat resistance is essential.

### 3.1.5.2. Heat deflection temperature

The heat deflection temperature (HDT) test results for the fabricated banana fiber-reinforced polyester composites are illustrated in Figure 10. The HDT values measured for the BFR, BFRR, BFRHM and BFRVM composites were 60 °C, 60 °C, 61 °C, and 64 °C, respectively. These results indicated that, while there was no significant difference in the HDT values among most of the composite types, the BFRVM-reinforced polyester composites exhibited a slightly higher HDT compared to the others.

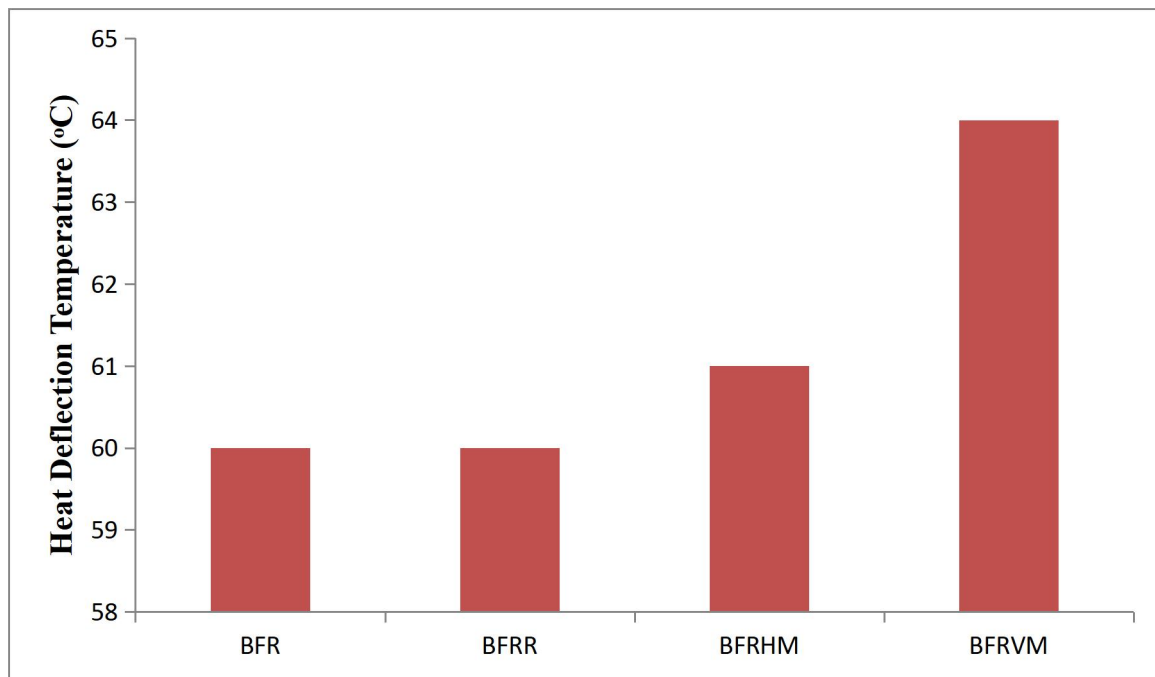

**Figure 10:** Heat deflection temperature test (HDT) for different forms of composites

The marginally higher HDT observed in the BFRVM composites, which registered at 64 °C, is attributed to the reinforcing effect of the banana fiber ropes used in the woven mat orientation. This enhanced HDT reflects the ability of the BFRVM composites to better maintain their rigidity and resist deformation under elevated temperatures. The increase in HDT for the BFRVM composites was particularly noteworthy, as it suggested improved thermal stability and durability of the material when exposed to high atmospheric temperatures. This characteristic was valuable for applications where the material was subjected to significant thermal stress, as it indicated that the composite withstands higher temperatures without experiencing substantial deflection or loss of structural integrity.

Overall, while the HDT values are relatively close among the four types of composites, the slight increase in HDT for BFRVM composites underscores the effectiveness of the mat form orientation in enhancing the thermal performance of the material. This makes BFRVM-reinforced polyester composites particularly suitable for environments where high-temperature resistance is crucial.

#### 4. Applications

The application of banana fiber rope mat composites in industrial components, presents a significant advancement in material sustainability and performance. Traditionally, industrial components are fabricated from metal, which was later replaced by glass fiber composites due to their lightweight and high-strength characteristics. However, glass fiber is not an eco-friendly material, leading to increased environmental concerns. Banana fiber rope mat composites offer an environmentally friendly alternative, leveraging the natural and renewable properties of banana fibers. The industrial components made from banana fiber rope mat composites exemplify this transition. The banana fiber rope mat provides excellent protection against mud and impacts, similarly to traditional materials, but with the added benefit of reduced environmental impact. This composite material not only matches the strength and durability required for effective industrial components protection, but also aligns with sustainable practices by utilizing natural fibers. The adoption of banana fiber rope mat composites in industrial components marks a progressive step towards integrating eco-friendly materials into industrial applications, thereby contributing to more sustainable manufacturing processes and reducing the overall environmental footprint of industrial components.

#### V. CONCLUSION

In the present investigation, a comprehensive analysis was conducted to evaluate the impact of banana fiber rope mat and random fiber orientations on the mechanical and thermal properties of polyester composites. The study revealed several key insights and conclusions regarding the performance of these composites. Notably, the

banana fiber rope vertical mat (BFRVM) reinforced polyester composites demonstrated superior mechanical strength, compared to the banana fiber random (BFR), banana fiber rope random (BFRR), and banana fiber rope horizontal mat (BFRHM) composites. This enhanced performance can be attributed to the mat orientation of the banana fiber rope, which facilitates a more uniform load distribution across the reinforcement, thereby improving the overall structural integrity and strength of the composite.

Scanning electron microscopy (SEM) analysis further supported these findings, showing that the adhesion between the banana fiber rope mat and the polyester matrix is notably effective. The interlocking of fibers within the mat structure enhances the bonding between the fiber and the matrix, contributing to the improved mechanical properties observed. The BFRVM composites not only exhibited better mechanical performance, compared to other natural fiber-reinforced composites, but also outperformed traditional glass fiber composites (GFC) in several aspects.

Thermal analysis revealed that the BFRVM composites have lower thermal conductivity compared to the other composite types, which can be attributed to the efficient packing arrangement of the banana fiber mat structure. This arrangement minimizes heat transfer, making the BFRVM composites more effective as thermal insulators. Additionally, the heat deflection temperature (HDT) of the BFRVM composites was slightly higher than that of the other composites. This improvement in HDT is due to the uniform distribution of fibers and strong adhesion between the banana fibers and the polyester matrix within the mat structure, which improves the material's ability to endure high temperatures without deforming.

Overall, the results of this investigation underscore the potential of banana fiber rope mat composites as a viable reinforcement material in polyester composites. These materials offer a combination of high strength, low thermal conductivity, and good heat resistance, which makes them suitable for applications such as industrial components. The findings suggest that banana fiber rope mat composites not only provide a cost-effective alternative to traditional materials, but also contribute to sustainable manufacturing practices by utilizing eco-friendly natural fibers.

#### **Acknowledgments**

The authors are grateful for the support rendered by Engr. Dr. George Onyeka Okoronkwo

#### **Funding**

No funding was received to assist with the preparation of this manuscript.

#### **Competing Interests**

The authors declare no competing interests.

#### **REFERENCES**

Akhil, U.V., Radhika, N., Saleh, B., Krishna, S.A., Noble, N., Rajeshkumar, L. (2023). A comprehensive review on plant-based natural fiber reinforced polymer composites: fabrication, properties, and applications. *Polymer Composite* 44, 2598–2633.

Akter M., Uddin, M. H., Anik H. R. (2024). Plant fiber-reinforced polymer composites: A review on modification, fabrication, properties, and applications. *Polymer Bulletin*, 81:1–85.

Bekraoui, N., El Qoubaa, Z., Chouiyakh, H., Faqir, M., Essadiqi, E. (2022). “Banana fiber extraction and surface characterization of hybrid banana reinforced composite”, *Journal of Natural Fibers*, 19/16, 12982-12995.

Ezeokpube Greg C., Okoronkwo George O, Onodagu Peter D. (2021). Natural fiber reggressors effects on physical and strength properties responses of bidirectional finger root fiber reinforced epoxy composites, *Journal of Inventive Engineering and Technology (JIET)*, A Publication of the Nigerian Society of Engineers, Awka Branch. Vol. 1, Issue 5, pp. 1-15.

Ezeokpube Greg C., Okoronkwo George O, Onodagu Peter D. (2021). Strength properties analysis of biomimetic natural wire weed fiber reinforced polymer composite honeycomb plates, *Journal of Inventive Engineering and Technology (JIET)*, A Publication of the Nigerian Society of Engineers, Awka Branch, Vol. 1, Issue 5, pp. 16-28.

Ezeokpube, G. E., Okoronkwo G. O., Madappa V. R. Sivasubramanian. (2019). Effects Of Strength Properties On Sisal-Fique-Areca Fibers-Reinforced Thermoset-Hybrid Composite Materials. *Oriental Journal of Science & Engineering* VOL -1, ISS-1.

Ezeokpube, G. E., Okoronkwo G. O., Madappa, V. R. Sivasubramanian. (2019). Micro-Hybridization Modelling and Analysis of Tensile and Flexural Strengths of Hybrid Bamboo-Coconut Reinforced Thermoset Composite Materials. *Oriental Journal of Science & Engineering* VOL -1, ISS-1.

George O. Okoronkwo and Chidobere David Nwa-David. (2025). Effects of Stacking Sequence and Mercerization treatment on Mechanical and Physical Properties of Hemp and Ramie-Reinforced Hybrid laminated Composites, *Nnamdi Azikiwe University Journal of Civil Engineering (NAUJCVE)*, Vol. 3, Issue 3, pp. 14-28.

George O. Okoronkwo and Chidobere David Nwa-David. (2025). Effect of Bio-composite hybridization stacking sequencing analysis on physical, mechanical and morphological behaviours of glass and Ukam fibre reinforced epoxy composites, *Nnamdi Azikiwe University Journal of Civil Engineering (NAUJCVE)*, Vol. 3, Issue 3, pp. 29-41.

George O. Okoronkwo and Chidobere David Nwa-David. (2025). The effects of fiber volume fractions and composite curing times on impact and hardness properties of areca fiber reinforced epoxy composites, *Nnamdi Azikiwe University Journal of Civil Engineering (NAUJCVE)*, Vol. 3, Issue 1, pp. 83-92.

George O. Okoronkwo, Chidobere David Nwa-David. (2024). Effect of ceramic filler materials on abrasive wear performance of glass/epoxy composites, *Advanced Journal of Engineering and Scientific Applications (AJESA)*, Vol. 1, Issue 1, pp. 16-28.

George O. Okoronkwo, Ibe Kizito Chidozie, Faloye Mayowa Emmanuel. (2025). Experimental Investigation of High Filler Loading of SiO<sub>2</sub> on the Mechanical and Dynamic Mechanical Analysis of Natural PALF fibre-Based Hybrid Composite, *Advanced Journal of Engineering and Scientific Applications (AJESA)*, Vol. 2, Issue 1, pp. 59-73.

George O. Okoronkwo, Ibe Kizito Chidozie, Obimba-Wogu Jesuborn. (2025). Experimental Investigations of Carbon Fiber Hybridization on Mechanical Strength Properties of Ramie Fiber Reinforced Epoxy Composite, *Advanced Journal of Engineering and Scientific Applications (AJESA)*, Vol. 2, Issue 1, pp. 45-58.

George O. Okoronkwo, Kizito Chidozie Ibe, Chidiebube Jeremiah Chukwu. (2025). Micro-structural analysis, optimization and RSM-based modelling for impact and flexural Micro-structural Analysis, Optimization and RSM-based Modeling for Impact and Flexural Strengths of Polymer Bio-composite Reinforced Epoxy Natural Fiber Materials, *Nnamdi Azikiwe University Journal of Civil Engineering (NAUJCVE)*, Vol. 3, Issue 1, pp. 93-104.

George O. Okoronkwo, Kizito Chidozie Ibe, Simeon I. Bright. (2022). Composite response comparative analysis, modeling, validations, and regressors effects on ramie fibre reinforced polyester material strength properties, *Journal of Inventive Engineering and Technology (JIET)*, A Publication of the Nigerian Society of Engineers, Awka Branch. Vol. 2, Issue 3, pp. 19-39.

George O. Okoronkwo, Kizito Chidozie Ibe, Simeon I. Bright. (2022). Application of ANN and RSM on the strength properties of alkali mercerized hybrid ramie-isora fibre reinforced biodegradable composites, *Journal of Inventive Engineering and Technology (JIET)*, A Publication of the Nigerian Society of Engineers, Awka Branch. Vol. 2, Issue 3, pp. 40-61.

George O. Okoronkwo, Nwadike Ethelbert C., Chukwudi Prince E. U. (2024). Effects of Graphene Nanoplatelets at low filler content on tensile and fracture toughness properties of f-GNP/epoxy Nanocomposites, *Advanced Journal of Engineering and Scientific Applications (AJESA)*, Vol. 1, Issue 1, pp. 1-15.

Hossain, M. S., Mobarak, M. B., Khan, A. T., Chowdhury, F., Ahmed, S. (2026). Sustainable synthesis of biocompatible nano-hydroxyapatite from seashell (micro-mollusk) waste. *RSC Advances*, 16 (4):3152–3162.

- Kamarudin, S. H., Mohd Basri, M. S., Rayung, M., Abu, F., Ahmad, S. B. (2022). A Review on Natural Fiber Reinforced Polymer Composites (NFRPC) for Sustainable Industrial Applications. *Polymers*, 14 (17), 3698.
- Kenned, J. J., Sankaranarayanan, K., Binoj, J. S., Chelliah, S. K. (2020). Thermo-mechanical and morphological characterization of needle punched non-woven banana fiber reinforced polymer composites. *Composite Science and Technology*, 185: 107890.
- Kusić, D., Božič, U., Monzón, M., Paz, R., Bordón, P. (2020). Thermal and Mechanical Characterization of Banana Fiber Reinforced Composites for Its Application in Injection Molding. *Materials*, 13 (16), 3581.
- Madu, K. E., Nwankwo, E. I., Okoronkwo, G. O., Onyewudiala, J.I. (2019). Micro-Mechanics Mercerization Analysis on the Tensile Strength and Interphase Quality of Stipa Stem Fibre-Reinforced Polypropylene Composite Materials. *Iconic Research and Engineering Journals*, Volume 3, Issue 5: 73 - 88.
- Madu, K. E., Nwankwo, E. I., Okoronkwo, G. O., Onyewudiala, J.I. (2020). Investigative Analysis of the Tensile and Impact Strengths of Hybridized Aluminum Metal Matrix Composite Materials. *Journal of Scientific Research and Reports*, 26(3): 72 - 79.
- Madu, K. E., Okoronkwo, G. O., Nwankwo, E. I. (2019). Analysis of Fique Fibre Thermo-set Vinyl-ester composite Flexural Strengths: *international Journal of Latest Engineering and Management Research*, Volume 04; Issue 06: Pp 60 - 66.
- Madu, K. E., Okoronkwo, G. O., Orji, M. E.K. (2019). Analysis of Areca Plant Stem Fibre Reinforced Polyester Thermo-set Composite Mechanical Properties. *International Journal of Engineering and Technical Research*, Volume - 9; Issue - 8: 28 - 32.
- Mahesh, D., Kowshigha, K. R., Raju, N. V., Aggarwal, P. K. (2020). Characterization of banana fiber reinforced polypropylene composite. *Journal of the Indian Academy of Wood Science*, vol. 17, no. 1, pp. 1-8.
- Manimaran, P., Pillai, G. P., Vignesh V., Prithiviraj, M. (2020). Characterization of natural cellulosic fibers from Nendran Banana Peduncle plants. *International Journal of Biological Macromolecules*, 162, 1807-1815 (2020).
- Okoronkwo G. O., Ifegbo A., N. (2021). The effects of regressors on tensile strength responses of rhus fiber reinforced thermoset composites, *Oriental Journal of Science and Engineering (OJSE)*, Vol.2, Issue 1, pp. 58-70.
- Okoronkwo, G. O., Madu, K. E., Nwankwo, E. I. (2019). Effects of Fibre Volume Fraction and Curing Time on Impact Hardness Strength Properties of Areca Fibres Reinforced Polyester Thermo-set Composites: *Research Journal of Mechanical Operations*, Volume 1; No. (2): Page(s) 31 - 37.
- Okoronkwo, G. O., Madu, K. E., Nwankwo, E., I. (2019). Analysis of fique fiber thermoset vinyl ester composite tensile and flexural strengths, *International journal of latest Engineering and Management Research (IJLEMR)*, ISSN: 2455-4847, Volume 04, Issue 06, pp. 60-66.
- Vignesh, V., Balaji, A. N., Nagaprasad, N., Sanjay, M. R., A. Khan, A. (2021). Indian mallow fiber reinforced polyester composites: mechanical and thermal properties. *Journal of Materials Research and Technology* Volume 11, Pages 274-284.